

viet nga

By qnujs

WORD COUNT

3702

TIME SUBMITTED

01-AUG-2025 01:59PM

PAPER ID

117523186

Tổng hợp composite $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ làm chất xúc tác quang hiệu năng cao phân hủy methylene blue

42 TÓM TẮT

Trong nghiên cứu này, vật liệu composite $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ được tổng hợp bằng cách chuẩn bị riêng biệt hai thành phần $\text{g-C}_3\text{N}_4$ và $\text{Co}_2[\text{Fe}(\text{CN})_6]$, sau đó kết hợp chúng thông qua quá trình phâ¹⁵n $\text{Co}_2[\text{Fe}(\text{CN})_6]$ lên bề mặt $\text{g-C}_3\text{N}_4$ ở 90 °C trong 1 giờ. Các vật liệu thu được được đặc trưng bằng các kỹ thuật nhiễu xạ tia X (XR³³ phô hồng ngoại biến đổi Fourier (FT-IR), phô tán xạ năng lượng tia X (EDS),³⁴ n vi điện tử quét (SEM), phô phản xạ khuếch tán UV-Vis (UV-Vis⁵⁴) và phô phát quang (PL). Hiệu suất xúc tác quâ⁵¹ của vật liệu composite được đánh giá thông qua quá trình phân hủy methylene¹⁴⁷ (MB) trong dung dịch nước dưới chiếu xạ ánh sáng mặt trời. Vật liệu composite $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ cho thấy hoạt tính xúc tác quang vượt trội so với từng thành phần riêng lẻ là $\text{g-C}_3\text{N}_4$ và $\text{Co}_2[\text{Fe}(\text{CN})_6]$.

Từ khóa: $\text{Co}_2[\text{Fe}(\text{CN})_6]$, $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$, photocatalytic activity, methylene blue, sunlight

Synthesis of $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite as an improved photocatalyst for degradation of methylene blue

ABSTRACT

In this study, the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite was synthesized by first preparing $\text{g-C}_3\text{N}_4$ and $\text{Co}_2[\text{Fe}(\text{CN})_6]$ separately,² followed by their coupling through the dispersion of $\text{Co}_2[\text{Fe}(\text{CN})_6]$ onto $\text{g-C}_3\text{N}_4$ at 90 °C for 1 hour. The resulting materials were characterized by X-ray diffraction (XRD), Fourier-transform infrared spectroscopy (FT-IR), energy-dispersive X-ray spectroscopy (EDS), and scanning electron microscopy (SEM), UV-Vis diffuse reflectance spectroscopy (UV-Vis DRS), and Photoluminescence (PL) spectroscopy. The photocatalytic performance of the composite was evaluated via³⁰ degradation of methylene blue (MB) in aqueous solution under sunlight irradiation. The $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ ¹² composite exhibited superior photocatalytic activity compared to the individual components, $\text{g-C}_3\text{N}_4$ and $\text{Co}_2[\text{Fe}(\text{CN})_6]$.

Keywords: $\text{Co}_2[\text{Fe}(\text{CN})_6]$, $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$, photocatalytic activity, methylene blue, sunlight.

1. INTRODUCTION

Faced with the growing reality of seriously polluted water sources that threaten both public health and the environment, various technologies have been developed for wastewater treatment. However, conventional methods often fail to completely eliminate toxic contaminants and typically require substantial energy input [1]. To align with the principles of sustainable chemistry, it is essential to develop more efficient reaction conditions and advanced catalytic systems for pollutant removal, thereby ensuring water quality [2]. Photocatalysis is a light-driven chemical process that occurs when a photocatalyst is activated by light irradiation. This technique has attracted significant attention due to its simplicity, cost-effectiveness, non-toxicity, high degradation efficiency, and long-term stability. It is widely regarded as a promising strategy for wastewater treatment and environmental protection [3].

In recent years, semiconductor materials such as TiO_2 , ZnO , SnO_2 , $\text{g-C}_3\text{N}_4$, and perovskites have been extensively investigated for photocatalytic applications in environmental remediation. Among emerging photocatalysts, $\text{Co}_x[\text{Fe}(\text{CN})_6]$ has attracted increasing attention and is gradually demonstrating its potential in photocatalysis, showing promise as a candidate for broad environmental applications.

Despite its outstanding advantages—such as strong visible-light absorption, non-toxicity to humans and other organisms, absence of secondary pollution, and ease of recyclability— $\text{Co}_x[\text{Fe}(\text{CN})_6]$ exhibits a major limitation: its high solubility in aqueous media. This characteristic poses significant challenges for its synthesis and practical application.

In 2013, Dwivedi et al. [4] employed gel beads containing cobalt hexacyanoferrate immobilized on micrometer-sized alginate beads (a salt of

alginic acid, $(\text{C}_6\text{H}_8\text{O}_6)$) as an adsorbent material for the removal of radioactive contaminants—such as cesium, an element with a half-life spanning several decades—from aqueous solutions. In 2016, K. A. Li²⁴ et al. [5] successfully synthesized a series of Prussian blue analogues with the general formula $\text{M}(\text{II})_3[\text{M}(\text{III})(\text{CN})_6]_2$ ($\text{M}^{2+} = \text{Co, Cu, Fe, Mn, Ni}$; $\text{M}^{3+} = \text{Co, Fe}$), which exhibited high photocatalytic activity. These materials were capable of efficiently degrading Rhodamine B (RhB) in aqueous solution when activated by peroxymonosulfate (PMS) under neutral conditions. Cobalt-based Prussian blue analogues (PBAs) have shown great potential as efficient catalysts for water-splitting reactions and the degradation of organic pollutants. Moreover, the Co-Fe PBAs retain their original crystalline structure even after multiple recycling cycles, indicating excellent structural stability.

Several studies have utilized metal-containing complexes and their isomers as polymeric materials. These isomeric complexes often exhibit cubic structures and feature metal ions in varying oxidation states [6]. The frameworks of these complexes possess porous structures, which endow them with a high specific surface area, excellent adsorption capacity, and numerous catalytic active sites. As a result, such complexes have been extensively studied across various fields, particularly in photocatalysis [7]. Therefore, the modification of these complexes with semiconductors to develop novel materials exhibiting enhanced photocatalytic activity has attracted significant attention from researchers.

2. EXPERIMENTS

2.1. Chemicals

Chemicals were purchased from Sigma-Aldrich (Germany) with high purity, including cobalt sulfate (CoSO_4 , ≥ 99.0%), potassium ferrocyanide ($\text{K}_4[\text{Fe}(\text{CN})_6]$, ≥ 98.5%), melamine ($\text{C}_3\text{H}_6\text{N}_6$, ≥ 99.0%), methylene blue hydrate

(C₁₆H₁₈ClN₃S.xH₂O, ≥ 91.0%), and ethanol (C₂H₅OH, ≥ 99.9%). All chemicals were used without further purification.

2.2. Materials preparation

2.2.1. Synthesis of g-C₃N₄: Five grams of melamine were ground in an agate mortar and then transferred to a porcelain crucible. The crucible was tightly covered with aluminum foil to minimize sublimation and enhance the condensation efficiency of g-C₃N₄. The sample was heated in a muffle furnace at 550 °C for 2 hours with a heating rate of 10 °C/min. After natural cooling to room temperature, the resulting product—yellowish in color—was collected and labeled as g-C₃N₄.

2.2.2. Synthesis of Co₂[Fe(CN)₆]: 5 milliliters of 0.2 M CoSO₄ solution were added to a 200 mL glass beaker. Then, 100 mL of 0.05 M K₄[Fe(CN)₆] solution were gradually added at a rate of 5 mL/min under continuous stirring at room temperature. A precipitate formed during the addition. The mixture was stirred for an additional 60 minutes, followed by ultrasonic treatment at 90 °C for 2 hours. The resulting solid was collected by centrifugation and washed repeatedly with distilled water until the pH of the filtrate reached 7. Finally, the sample was dried at 80 °C for 48 hours. The final product was identified as Co₂[Fe(CN)₆].

2.2.3. Synthesis of Co₂[Fe(CN)₆]/g-C₃N₄ composite: Cobalt sulfate (CoSO₄) was dissolved in deionized water under stirring until fully dissolved. A suitable amount of g-C₃N₄ powder was then added to the solution, followed by stirring and ultrasonication for 60 minutes at room temperature to promote the adsorption of Co²⁺ ions onto the g-C₃N₄ surface. The resulting suspension was centrifuged to collect the solid. Subsequently, a K₄[Fe(CN)₆] solution (with a mass ratio of 1:3 relative to the mass of g-C₃N₄) was added to the solid under continuous stirring at 90 °C for 60 minutes to allow in situ formation of the Co₂[Fe(CN)₆] framework on the g-C₃N₄ matrix. The product was separated by centrifugation, washed thoroughly, and dried at 80 °C for 48 hours to yield a blue solid of Co₂[Fe(CN)₆]/g-C₃N₄.

2.3. Characterization

X-ray diffraction (XRD) patterns were recorded using a Bruker D8 Advance diffractometer equipped with a Cu K α radiation source ($\lambda = 1.540 \text{ \AA}$), operating at 30 kV and 0.01 A. Fourier-transform infrared (FTIR) spectra were obtained using a PerkinElmer GX spectrometer. The

morphology and elemental composition of the samples were examined by scanning electron microscopy (SEM) and energy-dispersive X-ray spectroscopy (EDS) using a Nova Nano SEM 450 system. UV-Vis diffuse reflectance spectra (UV-Vis DRS) were measured using a Jasco V-770 spectrophotometer, while photoluminescence (PL) spectra were recorded on a Horiba Jobin Yvon FL322 fluorescence spectrometer. The concentration of MB solution was determined by a photometric method using a Jenway 6800 UV-Vis spectrophotometer.

2.4. Photocatalytic activity

The adsorption equilibrium time of MB on the materials was investigated under dark conditions using the following procedure. A total of 0.07 g of the material sample was added to a 250 mL beaker containing 120 mL of MB solution (10 mg/L). The beaker was covered with a wooden enclosure to prevent light exposure and continuously stirred using a magnetic stirrer. At 30-minute intervals, 8 mL of the suspension was withdrawn, centrifuged to separate the supernatant, and the resulting solution was transferred into a vial. The collected samples were labeled as $t_0, t_1, t_2, \dots, t_8$, corresponding to sampling times of 0, 30, 60, ..., and 240 minutes.

The adsorption capacity is calculated using the following equation:

$$q = \frac{(C_i - C_f) \cdot V}{m}$$

where q: adsorption capacity at a given time (mg/g); C_i: initial concentration of the solution (mg/L); C_f: concentration of the solution at the given time (mg/L); V: volume of the solution subjected to adsorption (L); m: mass of the adsorbent (g).

A plot of adsorption capacity versus time was drawn to determine the time required to reach adsorption equilibrium. Following the adsorption study, the sample was further exposed to sunlight to evaluate its photocatalytic activity. The degradation efficiency of MB by the materials was calculated using the following equation:

$$H = \frac{C_0 - C_t}{C_0} \times 100\%$$

where C₀ and C_t are the MB concentrations at the initial and selected t-times, respectively.

3. RESULTS AND DISCUSSIONS

3.1. Material characterization

7

The $\text{Co}_2[\text{Fe}(\text{CN})_6]$, g- C_3N_4 , and $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-}\text{C}_3\text{N}_4$ samples were characterized by XRD, FTIR, and SEM techniques.


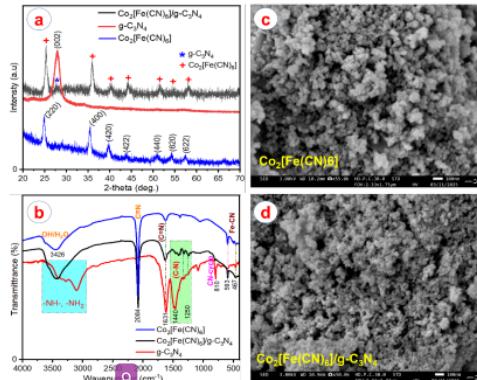


Figure 1. (a) XRD patterns; (b) FTIR spectra; (c, d) SEM images of $\text{Co}_2[\text{Fe}(\text{CN})_6]$, g- C_3N_4 , and the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-}\text{C}_3\text{N}_4$ composite

As shown in Fig. 1a, the XRD pattern of the $\text{Co}_2[\text{Fe}(\text{CN})_6]$ sample displays distinct diffraction peaks at $2\theta = 25.27^\circ$, 35.92° , 44.45° , 51.53° , 54.01° , and 58.38° , which correspond to the (220), (400), (422), (440), (620), and (622) crystal planes, respectively. These results are in good agreement with previous reports on $\text{Co}_2[\text{Fe}(\text{CN})_6]$. $\text{Co}_2[\text{Fe}(\text{CN})_6]$ exhibits high crystallinity with characteristic diffraction peaks corresponding to the Prussian blue analogue (PBA) phase, in accordance with JCPDS card No. 77-1161 [8, 9, 10]. The formation of the PBA-type $\text{Co}_2[\text{Fe}(\text{CN})_6]$ material from its precursors can be represented by the following reaction equation:



The XRD pattern of pure g- C_3N_4 exhibits a prominent diffraction peak at $2\theta = 27.4^\circ$, which corresponds to the (002) crystal plane. This peak is attributed to the interlayer stacking of conjugated aromatic systems in the graphitic carbon nitride structure. The $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-}\text{C}_3\text{N}_4$ composite clearly exhibits the characteristic diffraction peaks of both constituent materials, $\text{Co}_2[\text{Fe}(\text{CN})_6]$ and g- C_3N_4 . Moreover, no additional crystalline phases are detected, indicating that the composite consists solely of these two components. This result is consistent with previously reported studies on PBA/g- C_3N_4 materials [8].

The FTIR spectra of the samples are presented in Fig. 1b. The g- C_3N_4 sample exhibits a distinct absorption band at 810 cm^{-1} , which is attributed to the out-of-plane bending vibration of C-N bonds within the tri-s-triazine (heptazine) units—the

fundamental structural motifs of the graphitic carbon nitride framework [11, 12]. The sharp absorption bands in the region of 1250 – 1631 cm^{-1} are attributed to the stretching vibrations of C-N and C≡N bonds within the aromatic rings of the heptazine-based structure [13]. In addition, a broad absorption band in the range of 3100 – 3400 cm^{-1} is observed, which is attributed to the stretching vibrations of $-\text{NH}-$ and $-\text{NH}_2$ groups originating from the incompletely condensed structure of g- C_3N_4 . The FTIR spectrum of $\text{Co}_2[\text{Fe}(\text{CN})_6]$ displays several characteristic absorption bands. A strong and sharp peak at 2084 cm^{-1} is attributed to the stretching vibration of the C≡N bond in the imide ligands, while a prominent band at 593 cm^{-1} corresponds to the bending vibration of the same group. Additionally, the absorption band at 467 cm^{-1} is ascribed to the stretching vibration of the Fe-CN bond [14], confirming the metal-ligand coordination typical of Prussian Blue analogues (PBAs). Furthermore, a broad absorption band centered around 3426 cm^{-1} is associated with the $-\text{OH}$ stretching vibration of water molecules adsorbed on the material surface. For the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-}\text{C}_3\text{N}_4$ composite, the characteristic peaks corresponding to both g- C_3N_4 and $\text{Co}_2[\text{Fe}(\text{CN})_6]$ were clearly observed, indicating the successful integration of the two components. In particular, the intense absorption band at 2084 cm^{-1} (assigned to the $-\text{C}\equiv\text{N}$ stretching vibration) remained prominent, while the C-N and C≡N stretching vibrations of g- C_3N_4 were also retained. These observations confirm that the key structural features of both phases were preserved in the composite. Moreover, the absence of new absorption bands or significant peak shifts suggests that the interaction between $\text{Co}_2[\text{Fe}(\text{CN})_6]$ and g- C_3N_4 is primarily physical in nature, possibly involving electrostatic attractions or hydrogen bonding. This result is in good agreement with the XRD data.

The SEM images of the $\text{Co}_2[\text{Fe}(\text{CN})_6]$ sample (Fig. 1c) and the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-}\text{C}_3\text{N}_4$ composite (Fig. 1d) reveal distinct morphological characteristics. The pristine $\text{Co}_2[\text{Fe}(\text{CN})_6]$ exhibits a granular morphology composed of irregularly shaped, densely packed nanoparticles with a pronounced tendency toward agglomeration. The surface of the material appears relatively rough and compact, which may limit the accessibility of active sites for catalytic processes. In contrast, the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-}\text{C}_3\text{N}_4$ composite exhibited a more porous architecture with significantly reduced particle agglomeration. The nanoparticles were more uniformly dispersed, with increased interparticle voids, likely attributed to the structural support provided by the g- C_3N_4 matrix.

This morphology suggests enhanced textural properties, such as a larger specific surface area and improved accessibility to active sites—factors that are critical for adsorption and photocatalytic performance. The morphological differences between the two samples provide clear evidence for the successful incorporation of $\text{Co}_2[\text{Fe}(\text{CN})_6]$ into the $\text{g-C}_3\text{N}_4$ matrix. This integration effectively suppresses excessive particle agglomeration, enhances interfacial contact, and facilitates charge transfer during the photocatalytic process. These observations are consistent with the XRD and FTIR analyses, further confirming the formation of a structurally and functionally synergistic composite material.

The EDS spectra in Fig. 2 and Table 1 confirm the elemental composition of the samples.

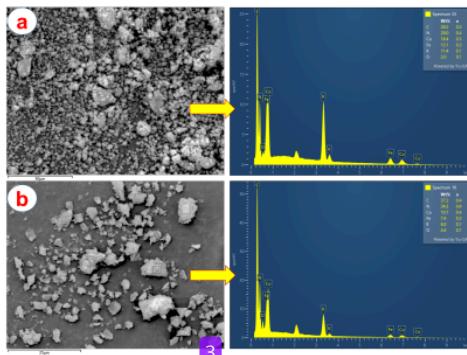


Figure 2. EDS spectra of (a) the $\text{Co}_2[\text{Fe}(\text{CN})_6]$ sample and (b) the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite

Both the $\text{Co}_2[\text{Fe}(\text{CN})_6]$ and $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ samples exhibit characteristic peaks of Co, Fe, C, and N, consistent with the expected structure of Prussian Blue analogues (PBA). Additionally, minor signals of K and O are observed. The presence of K is attributed to residual $\text{K}_4[\text{Fe}(\text{CN})_6]$ precursor, while the O signal likely originates from surface-adsorbed moisture (H_2O). In the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite, the increased intensities of C and N peaks are ascribed to the contribution of the $\text{g-C}_3\text{N}_4$ matrix, while the decreased Co and Fe contents suggest effective dispersion of the PBA phase on the $\text{g-C}_3\text{N}_4$ surface. These findings confirm the successful formation of the composite material.

Table 1. Elemental composition of $\text{Fe}_3[\text{Fe}(\text{CN})_6]_2$ and $\text{Fe}_3[\text{Fe}(\text{CN})_6]_2/\text{g-C}_3\text{N}_4$

$\text{Co}_2[\text{Fe}(\text{CN})_6]$		$\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$	
Element	Weight%	Element	Weight%
C	29.2	C	37.2

N	29.0	N	34.3
Co	16.4	Co	10.7
Fe	12.1	Fe	7.4

The EDS-mapping (Fig. 40) results show that Co, Fe, C, and N elements are uniformly distributed across the sample surface, indicating the successful integration and homogeneous dispersion of $\text{Co}_2[\text{Fe}(\text{CN})_6]$ within the $\text{g-C}_3\text{N}_4$ matrix. No significant aggregation or phase separation was observed, suggesting strong interfacial compatibility between the two components. This uniform distribution supports the structural integrity of the composite and correlates well with the results obtained from XRD, FTIR, and SEM, reinforcing the successful synthesis of a well-dispersed hybrid photocatalyst.


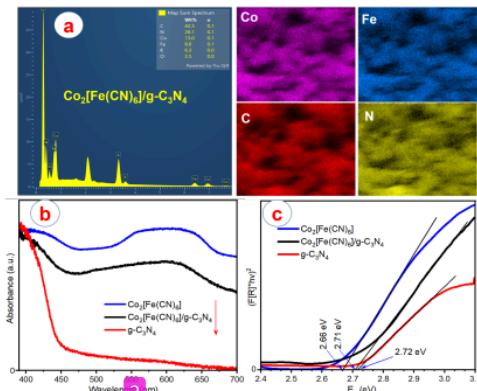


Figure 3. (a) Elemental mapping images of Co, C, and N for the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite, (b) UV-Vis DRS spectra and (b) band gap energy of the materials

The UV-Vis DRS (Fig. 3b,c) reveal that all the materials exhibit absorption edges within the visible light region. Notably, the $\text{Co}_2[\text{Fe}(\text{CN})_6]$ and $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ samples show extended absorption edges reaching up to approximately 700 nm, which is consistent with the characteristic charge transfer transitions between Fe(II) and Fe(III) [15].



The band gap energy (E_g) of the materials was also estimated using the Tauc method. Accordingly, the band gap values of $\text{Co}_2[\text{Fe}(\text{CN})_6]$, $\text{g-C}_3\text{N}_4$, and the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite were determined to be 2.66 eV, 2.72 eV, and 2.71 eV, respectively.

3.2. Photocatalytic activity

The photocatalytic performance of the materials was evaluated through the degradation of MB under sunlight irradiation, with the results

illustrated in Fig. 4a. After 210 minutes of exposure, the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite exhibited a degradation efficiency of 93.38%, outperforming both pristine $\text{g-C}_3\text{N}_4$ and $\text{Co}_2[\text{Fe}(\text{CN})_6]$ (Fig. 4b). In addition, to compare the MB degradation rates among the materials, the kinetics of MB photodegradation were investigated (Fig. 4c and Table 2). Under identical illumination conditions, the degradation rate of MB using the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite was approximately 16 times higher than that of $\text{Co}_2[\text{Fe}(\text{CN})_6]$ and more than 19 times higher than that of pristine $\text{g-C}_3\text{N}_4$. This significant enhancement is attributed to the effective suppression of the rapid recombination of photogenerated electron-hole pairs, a common limitation in single-component $\text{g-C}_3\text{N}_4$ photocatalysts, as confirmed by the photoluminescence (PL) spectra shown in Fig. 4d. The photoluminescence (PL) spectra of $\text{g-C}_3\text{N}_4$ and the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite were recorded under 365 nm excitation to evaluate the separation and recombination behavior of photoinduced electron-hole pairs (e^-/h^+). In the spectrum, pristine $\text{g-C}_3\text{N}_4$ exhibits a strong emission peak around 400–550 nm, which is indicative of the rapid recombination of photogenerated charge carriers. Notably, the PL intensity of the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite is significantly quenched compared to pure $\text{g-C}_3\text{N}_4$. This pronounced reduction in emission intensity suggests that the incorporation of $\text{Co}_2[\text{Fe}(\text{CN})_6]$ effectively suppresses the recombination of charge carriers. As an efficient electron acceptor, $\text{Co}_2[\text{Fe}(\text{CN})_6]$ facilitates charge transfer and enhances charge separation at the heterojunction interface with $\text{g-C}_3\text{N}_4$. In summary, the PL analysis confirms that the formation of the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite improves electron-hole separation and reduces charge recombination, thereby enhancing the photocatalytic performance by making more charge carriers available for surface reactions. This property broadens the potential applications of the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite in the field of photocatalysis.

Table 2. Results of MB degradation by the materials

Materials	Photodegradation (%)	20 Rate constant, k (min^{-1})	Regression coefficient (R^2)
$\text{g-C}_3\text{N}_4$	13.91	$0.06 \cdot 10^{-2}$	0.95
$\text{Co}_2[\text{Fe}(\text{CN})_6]$	38.74	$0.24 \cdot 10^{-2}$	0.99

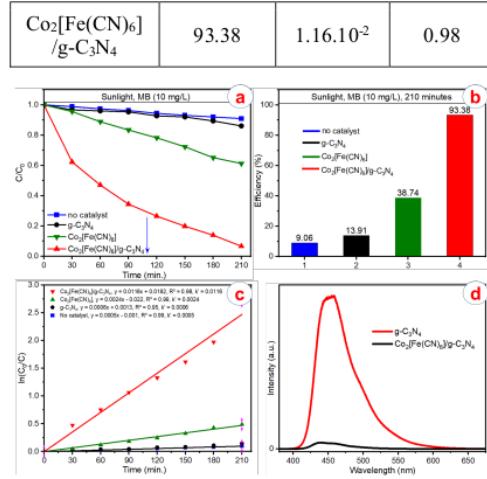


Figure 4. (a–c) Photocatalytic degradation of MB over $\text{Co}_2[\text{Fe}(\text{CN})_6]$, $\text{g-C}_3\text{N}_4$, and $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$; (d) PL spectra of the corresponding materials

3.3. Photocatalytic reaction mechanism

To investigate the photocatalytic reaction mechanism, various scavengers were employed to identify the main reactive species involved. Tert-butyl alcohol (TBA) was used as a scavenger for hydroxyl radicals ($\cdot\text{OH}$), 1,4-benzoquinone (BQ) for superoxide radical anions ($\cdot\text{O}_2^-$), ammonium oxalate (AO) for photogenerated holes (h^+), and dimethyl sulfoxide (DMSO) for photogenerated electrons (e^-) [16]. A quenching agent solution with an initial concentration of 10 mmol/L and a volume of 2 mL was added at the onset of light irradiation. As shown in Fig. 5a, the presence of TBA and AO led to a noticeable decrease in the photocatalytic degradation of MB by the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite, compared to the control sample without any scavenger. This can be attributed to the quenching effects of ammonium oxalate (AO) on photogenerated holes (h^+) and of 1,4-benzoquinone (BQ) on superoxide radical anions ($\cdot\text{O}_2^-$), which significantly suppressed the activity of these reactive species in solution and thus reduced photocatalytic efficiency. These findings suggest that h^+ and $\cdot\text{O}_2^-$ are the primary active species responsible for the MB degradation process. Thus, the integration of $\text{Co}_2[\text{Fe}(\text{CN})_6]$ and $\text{g-C}_3\text{N}_4$ into a composite structure resulted in $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$, which possesses critical properties for facilitating the generation of h^+ and $\cdot\text{O}_2^-$ radicals, while simultaneously suppressing the recombination of photogenerated electron-hole pairs during the photocatalytic degradation of MB.

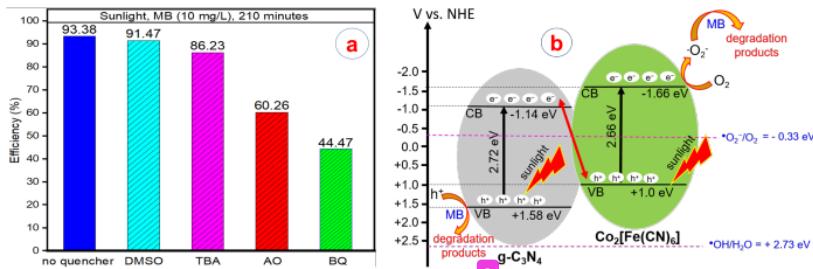


Figure 5. (a) Photocatalytic degradation of MB on Co₂[Fe(CN)₆]/g-C₃N₄ in the presence of various scavengers, and (b) Proposed Z-scheme mechanism for the photocatalytic activity of the Co₂[Fe(CN)₆]/g-C₃N₄ composite

43 The valence band (VB) and conduction band (CB) positions of g-C₃N₄ and Co₂[Fe(CN)₆] can be estimated using the following equations:

$$E_{VB} = \chi - E^{\circ} + 0.5E_g$$

$$E_{CB} = E_{VB} - E_g$$

44 where χ is the absolute electronegativity of the semiconductor (defined as the arithmetic mean of the electron affinity and the first ionization energy of the constituent atoms), E° is the energy of free electrons on the hydrogen scale (4.5 eV), and E_g is the band gap energy of the semiconductor.

According to Wu et al. [17], the absolute electronegativity (χ) of g-C₃N₄ is 4.72 eV. Based on Mulliken's theory, the electronegativity χ of a semiconductor can be accurately calculated using the following formula:

$$\chi = E_{vacuum} - \frac{E_g}{2}$$

Applied to Co₂[Fe(CN)₆]:

+ $E_g \approx 2.66$ eV (as determined from the UV-Vis DRS spectra)






+ $E_{vacuum} \approx 5.5$ eV [18]

The calculated absolute electronegativity (χ) is 4.17 eV.

18 Based on the calculations, the conduction band (CB) and valence band (VB) edge potentials of g-C₃N₄ are estimated to be -1.14 eV and +1.58 eV, respectively. Similarly, the CB and VB edge potentials of Co₂[Fe(CN)₆] are calculated to be -1.66 eV and +1.00 eV respectively.

On this basis, the separation of photogenerated electron-hole pairs and the formation of reactive radicals in the Co₂[Fe(CN)₆]/g-C₃N₄ composite under illumination are illustrated in Fig. 5b (Z-scheme). Under light irradiation, both semiconductor materials are photoexcited and generate electron-hole pairs. The photogenerated electrons in the conduction band (CB) of g-C₃N₄ tend to recombine with the holes in the valence

band (VB) of Co₂[Fe(CN)₆]. This combination occurs at the contact interface, leading to the accumulation of electrons in the conduction band (CB) of Co₂[Fe(CN)₆] and holes in the valence band (VB) of g-C₃N₄. Consequently, the photogenerated charge carriers are spatially separated across the two semiconductors, while maintaining strong redox potentials. The electrons in the conduction band (CB) of Co₂[Fe(CN)₆] reduce O₂ to superoxide radicals (·O₂⁻), which subsequently contribute to the degradation of MB. In contrast, the holes in the valence band (VB) of g-C₃N₄, due to their insufficient oxidation potential, are unable to oxidize H₂O to generate hydroxyl radicals (·OH), but can directly oxidize MB molecules. Accordingly, the photocatalytic degradation of MB may involve the following processes:



8 This mechanism satisfactorily explains the reduced recombination of photogenerated electron-hole pairs on the g-C₃N₄ component of the Co₂[Fe(CN)₆]/g-C₃N₄ composite, as confirmed by the photoluminescence (PL) analysis (Fig. 4d) and the photocatalytic performance results (Fig. 5a). This suppression of large carrier recombination subsequently enhances the photocatalytic degradation efficiency of MB by the composite under light irradiation.

4. CONCLUSIONS

3 Nano-sized Co₂[Fe(CN)₆] and the Co₂[Fe(CN)₆]/g-C₃N₄ composite were successfully synthesized. The corresponding band gap energies were determined to be 2.66 eV for Co₂[Fe(CN)₆], 2.72 eV for g-C₃N₄, and 2.71 eV for the composite. Under natural sunlight irradiation for 210 minutes,

the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite exhibited a photocatalytic degradation efficiency of 93.38% for methylene blue in aqueous solution, significantly outperforming the individual components $\text{Co}_2[\text{Fe}(\text{CN})_6]$ and $\text{g-C}_3\text{N}_4$. The enhanced photocatalytic performance of the composite is mainly attributed to the effective

suppression of photogenerated electron–hole recombination. A Z-scheme mechanism for the photocatalytic degradation of methylene blue by the $\text{Co}_2[\text{Fe}(\text{CN})_6]/\text{g-C}_3\text{N}_4$ composite was proposed and discussed in detail by the authors.

32%

SIMILARITY INDEX

PRIMARY SOURCES

1	www.mdpi.com Internet	170 words — 4%
2	Wee-Jun Ong, Lling-Lling Tan, Yun Hau Ng, Siek-Ting Yong, Siang-Piao Chai. " Graphitic Carbon Nitride (g-C N)-Based Photocatalysts for Artificial Photosynthesis and Environmental Remediation: Are We a Step Closer To Achieving Sustainability? ", Chemical Reviews, 2016 <small>Crossref</small>	135 words — 3%
3	T.P. Valsala, Annie Joseph, J.G. Shah, Kanwar Raj, V. Venugopal. "Synthesis and characterization of cobalt ferrocyanides loaded on organic anion exchanger", Journal of Nuclear Materials, 2009 <small>Crossref</small>	83 words — 2%
4	Zhao, D. F., H. Yang, R. S. Li, J. Y. Ma, and W. J. Feng. "Fabrication of nickel ferrite-graphene nanocomposites and their photocatalytic properties", Materials Research Innovations, 2014. <small>Crossref</small>	61 words — 1%
5	pubs.rsc.org Internet	57 words — 1%
6	www.science.gov Internet	53 words — 1%
7	O. V. Mikhailov. "Immobilization of (dd)heteronuclear hexacyanoferrates(II) in a gelatin matrix", Russian Chemical Bulletin, 01/2008	43 words — 1%

8 www.sciencegate.app 39 words — 1 %
Internet

9 link.springer.com 38 words — 1 %
Internet

10 worldwidescience.org 32 words — 1 %
Internet

11 Feixue Sun, Lixiang Chen, Xinlong Fan, Zihui Meng, 31 words — 1 %
Wenfang Liu. "Aniline or potassium
hexacyanoferrate engineering graphitic carbon nitride for
highly efficient photocatalytic NADH regeneration", Journal of
Environmental Chemical Engineering, 2025
Crossref

12 Rasmussen, P.G.. "An investigation of Prussian Blue 30 words — 1 %
analogues by Mossbauer spectroscopy and magnetic
susceptibility", Polyhedron, 1984
Crossref

13 downloads.hindawi.com 23 words — 1 %
Internet

14 Vy Anh Tran, Ha Tran Huu, Hong Nhungh Thi Ngo, Van 22 words — 1 %
Ngoc Ngo et al. "Magnesiothermic reduction
synthesis of N-deficient g-C3N4 with enhanced photocatalytic
performance under visible light", Chemical Physics, 2023
Crossref

15 jst-ud.vn 22 words — 1 %
Internet

16 repositorio.uam.es 22 words — 1 %
Internet

17 websrv2.dthu.edu.vn 19 words — < 1 %
Internet

18 www.tandfonline.com
Internet 19 words – < 1 %

19 assets.researchsquare.com
Internet 17 words – < 1 %

20 iopscience.iop.org
Internet 17 words – < 1 %

21 static.frontiersin.org
Internet 17 words – < 1 %

22 Hui Zhao, Junwei Wang, Yuming Dong, Pingping Jiang. "Noble-Metal-Free Iron Phosphide Cocatalyst Loaded Graphitic Carbon Nitride as an Efficient and Robust Photocatalyst for Hydrogen Evolution under Visible Light Irradiation", *ACS Sustainable Chemistry & Engineering*, 2017
Crossref 16 words – < 1 %

23 libjncir.jncasr.ac.in
Internet 16 words – < 1 %

24 www.mrs.org
Internet 16 words – < 1 %

25 www.pjoes.com
Internet 16 words – < 1 %

26 "Iron through Hassium", *Inorganic Reactions in Water*, 2008
Crossref 14 words – < 1 %

27 Olalekan C. Olatunde, Damian C. Onwudiwe. "A Comparative Study of the Effect of Graphene Oxide, Graphitic Carbon Nitride, and Their Composite on the Photocatalytic Activity of Cu₃SnS₄", *Catalysts*, 2021
Crossref 14 words – < 1 %

28 Manjot Kaur, Ahmad Umar, Surinder Kumar Mehta, Sushil Kumar Kansal. "Reduced graphene oxide-CdS heterostructure: An efficient fluorescent probe for the sensing of Ag(I) and sunset yellow and a visible-light responsive photocatalyst for the degradation of levofloxacin drug in aqueous phase", *Applied Catalysis B: Environmental*, 2018
Crossref 13 words – < 1 %

29 Ruihan Liu, Jingkun Yu, Zhaodi Wang, Yonggang Liu, Yunpu Zhai. "Ultra-thin MXene-induced built-in electric field enhances Mo-doped FeCo-layered double hydroxides for water splitting at high current densities", *Journal of Colloid and Interface Science*, 2025
Crossref 13 words – < 1 %

30 Avramenko, V.. "Colloid stable sorbents for cesium removal: Preparation and application of latex particles functionalized with transition metals ferrocyanides", *Journal of Hazardous Materials*, 20110228
Crossref 12 words – < 1 %

31 Nga Nguyen Thi Viet, Tram Do Thi Hong, Nhat Nguyen Bich, Giang Tran Chau, Thinh Tran Dinh, Tam Truong Thanh, Kim Nguyen Van. "Synthesis and photocatalytic activity of ZnO/g-C3N4 materials under visible light", *Vietnam Journal of Catalysis and Adsorption*, 2021
Crossref 12 words – < 1 %

32 bura.brunel.ac.uk 12 words – < 1 %
Internet

33 tailieu.vn 12 words – < 1 %
Internet

34 Do Dang Tran, Minh Nhat Dang, Chau Ngoc Chu, Noi Van Nguyen et al. "Synthesis of Z-scheme heterostructure FeWO4/rGO/g-C3N4 as a visible-light 11 words – < 1 %

35 Nguyen Thi Minh Tam, Yunguo Liu, Hassan Bashir, Zhihong Yin, Yuan He, Xudong Zhou. "Efficient Removal of Diclofenac from Aqueous Solution by Potassium Ferrate-Activated Porous Graphitic Biochar: Ambient Condition Influences and Adsorption Mechanism", International Journal of Environmental Research and Public Health, 2019
[Crossref](#) 11 words – < 1 %

36 coek.info Internet 11 words – < 1 %

37 repositorio.unesp.br Internet 11 words – < 1 %

38 repository.kulib.kyoto-u.ac.jp Internet 11 words – < 1 %

39 www.zigya.com Internet 11 words – < 1 %

40 Nan Li, Jiaming Li, Jiaqi Li, Changfu Ma et al. "Zeolite-coated separator suppresses manganese dissolution by selective ion trapping for long-cycling alkaline batteries", Chemical Engineering Science, 2026
[Crossref](#) 10 words – < 1 %

41 Shengtian Huang, Junbo Zhong, Jianzhang Li, Jiufu Chen, Zhen Xiang, Wei Hu, Minjiao Li. "Z-scheme TiO₂ /g-C₃N₄ composites with improved solar-driven photocatalytic performance deriving from remarkably efficient separation of photo-generated charge pairs", Materials Research Bulletin, 2016
[Crossref](#) 10 words – < 1 %

42 Internet 10 words – < 1 %

43 iehpc.gdut.edu.cn Internet 10 words – < 1 %

44 js.vnu.edu.vn Internet 10 words – < 1 %

45 www.coursehero.com Internet 10 words – < 1 %

46 www.imedpub.com Internet 10 words – < 1 %

47 Nga Tran Thi Viet, Truong Tran Ngoc Thien, Luong Nguyen Van, Lien Hoang Nu Thuy, Kim Nguyen Van. "Synthesis and photocatalytic activity of g-C3N4/CdS materials under visible light", Vietnam Journal of Catalysis and Adsorption, 2022 9 words – < 1 %
Crossref

48 Parlak, Onur, Preethi Seshadri, Ingemar Lundström, Anthony P. F. Turner, and Ashutosh Tiwari. "Two-Dimensional Gold-Tungsten Disulphide Bio-Interface for High-Throughput Electrocatalytic Nano-Bioreactors", Advanced Materials Interfaces, 2014. 9 words – < 1 %
Crossref

49 Sangeeta Adhikari, Debasish Sarkar, Giridhar Madras. "Hierarchical Design of CuS Architectures for Visible Light Photocatalysis of 4-Chlorophenol", ACS Omega, 2017 9 words – < 1 %
Crossref

50 Yongchun Ye, Hua Yang, Haimin Zhang, Jinling Jiang. "A promising Ag CrO /LaFeO heterojunction photocatalyst applied to photo-Fenton degradation of RhB", Environmental Technology, 2018 9 words – < 1 %
Crossref

51 chemeng.hust.edu.vn Internet 9 words – < 1 %

52 www.researchgate.net Internet 9 words – < 1 %

53 Haifeng Shi. "NaNbO₃ Nanostructures: Facile Synthesis, Characterization, and Their Photocatalytic Properties", *Catalysis Letters*, 07/16/2009 Crossref 8 words – < 1 %

54 Nga Viet Thi Nguyen, Hang Thanh Le Nguyen, Thanh Thi Ho, Lieu Thanh Thi Le, Lan Thi Nguyen, Thuat Ngoc Pham, Kim Van Nguyen. "Photocatalytic degradation of methylene blue from an aqueous solution using SnO₂/BaTiO₃ heterostructure", *Vietnam Journal of Catalysis and Adsorption*, 2023 Crossref 8 words – < 1 %

55 Sandra Stets, Bianca do Amaral, Jéssica Tamara Schneider, Ivan Ricardo de Barros et al. "Antituberculosis drugs degradation by UV-based advanced oxidation processes", *Journal of Photochemistry and Photobiology A: Chemistry*, 2018 Crossref 8 words – < 1 %

56 Surbhi Kapoor, Vinod Kumar, K.B. Tikoo, Bhupendra Chudasama, Neetu Goel, Sonal Singhal. "Strategically designed reduced graphene oxide based magnetic responsive nanocatalysts for the attenuation of recalcitrant pollutants", *Ceramics International*, 2020 Crossref 8 words – < 1 %

57 Xiaofei Yang, Hua Tang, Jingsan Xu, Markus Antonietti, Menny Shalom. "Silver Phosphate/Graphitic Carbon Nitride as an Efficient Photocatalytic Tandem System for Oxygen Evolution", *ChemSusChem*, 2015 Crossref 8 words – < 1 %

58 Yan, H.. "Synthesis of graphitic carbon nitride by directly heating sulfuric acid treated melamine for enhanced photocatalytic H² production from water under visible light", International Journal of Hydrogen Energy, 201201
Crossref 8 words – < 1 %

59 mdpi-res.com Internet 8 words – < 1 %

60 pubmed.ncbi.nlm.nih.gov Internet 8 words – < 1 %

61 ruor.uottawa.ca Internet 8 words – < 1 %

62 www.frontiersin.org Internet 8 words – < 1 %

63 Tang, Zi-Rong, Xia Yin, Yanhui Zhang, and Yi-Jun Xu. "Synthesis of Titanate Nanotube–CdS Nanocomposites with Enhanced Visible Light Photocatalytic Activity", Inorganic Chemistry, 2013. 6 words – < 1 %
Crossref

EXCLUDE QUOTES

OFF

EXCLUDE BIBLIOGRAPHY

OFF

EXCLUDE SOURCES

OFF

EXCLUDE MATCHES

OFF